

HASTELLOY® C-276 Alloy

Hydrobromic Acid

Conc. Wt.%	50°F	75°F	100°F	125°F	150°F	175°F	200°F	225°F	Boil- ing
	10°C	24°C	38°C	52°C	66°C	79°C	93°C	107°C	
2.5	-	-	-	-	-	-	-	-	0.13
5	-	-	-	-	-	0.01	0.15	-	0.78
7.5	-	-	-	-	0.01	0.14	0.73	-	-
10	-	-	-	-	0.02	0.51	0.89	-	-
15	-	-	-	0.01	0.34	0.57	-	-	-
20	-	-	<0.01	0.25	0.37	0.51	-	-	-
25	-	-	0.11	0.2	0.29	0.45	0.75	-	-
30	-	-	0.12	0.2	0.28	0.44	0.75	-	-
40	-	-	0.08	0.13	0.21	0.3	0.53	-	-


All corrosion rates are in millimeters per year (mm/y); to convert to mils (thousandths of an inch) per year, divide by 0.0254.

Data are from Corrosion Laboratory Jobs 15-02, 27-02, and 37-02.

All tests were performed in reagent grade acids under laboratory conditions; field tests are encouraged prior to industrial use.

HASTELLOY® C-276 Alloy

Iso-Corrosion Diagram for C-276 Alloy in Hydrobromic Acid

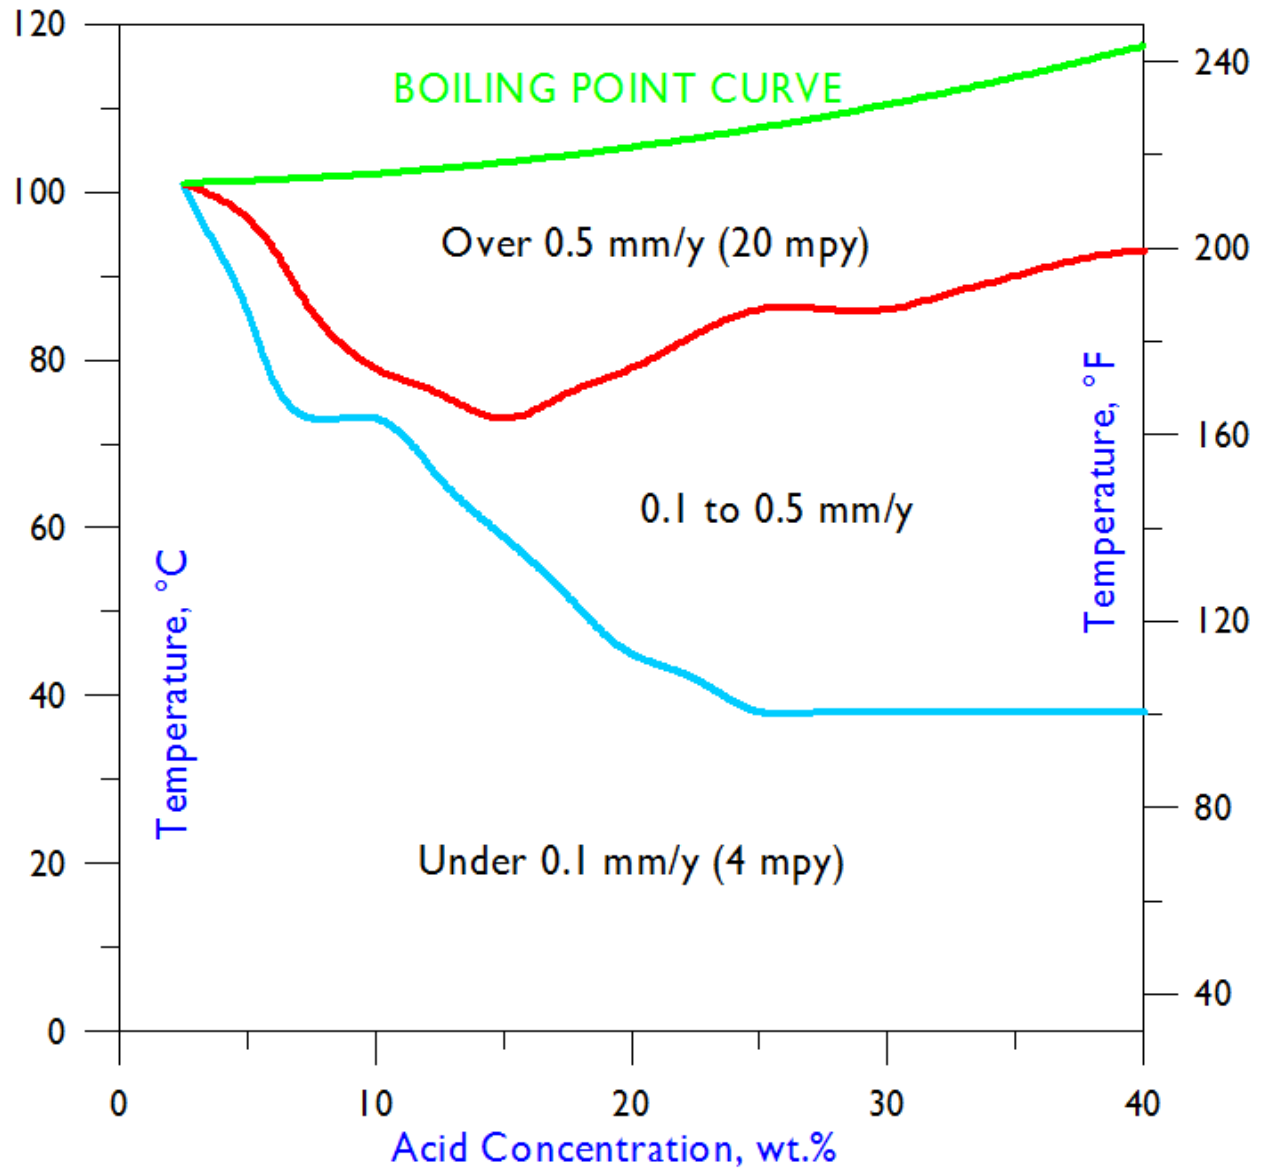

When using this data, please refer to our disclaimer located at www.haynesintl.com