

HASTELLOY® G-35® Alloy

Hydrochloric Acid

Conc. Wt.%	50°F	75°F	100°F	125°F	150°F	175°F	200°F	225°F	Boiling
	10°C	24°C	38°C	52°C	66°C	79°C	93°C	107°C	
1	-	-	-	-	-	-	-	-	0.05
1.5	-	-	-	-	-	-	-	-	-
2	-	-	-	-	-	-	<0.01	-	0.05
2.5	-	-	-	<0.01	<0.01	<0.01	17.83	-	-
3	-	-	-	-	<0.01	<0.01	-	-	-
3.5	-	-	-	-	-	-	-	-	-
4	-	-	-	-	-	-	-	-	-
4.5	-	-	-	-	-	-	-	-	-
5	-	-	<0.01	-	<0.01	1.23	17.08	-	-
7.5	-	-	<0.01	0.47	0.97	-	-	-	-
10	-	<0.01	0.17	1.49	-	-	-	-	-
15	0.09	0.19	0.52	-	-	-	-	-	-
20	0.08	0.15	0.42	-	-	-	-	-	-


All corrosion rates are in millimeters per year (mm/y); to convert to mils (thousandths of an inch) per year, divide by 0.0254.

Data are from Corrosion Laboratory Job 44-02.

All tests were performed in reagent grade acids under laboratory conditions; field tests are encouraged prior to industrial use.

HASTELLOY® G-35® Alloy

Iso-Corrosion Diagram for G-35 Alloy in Hydrochloric Acid

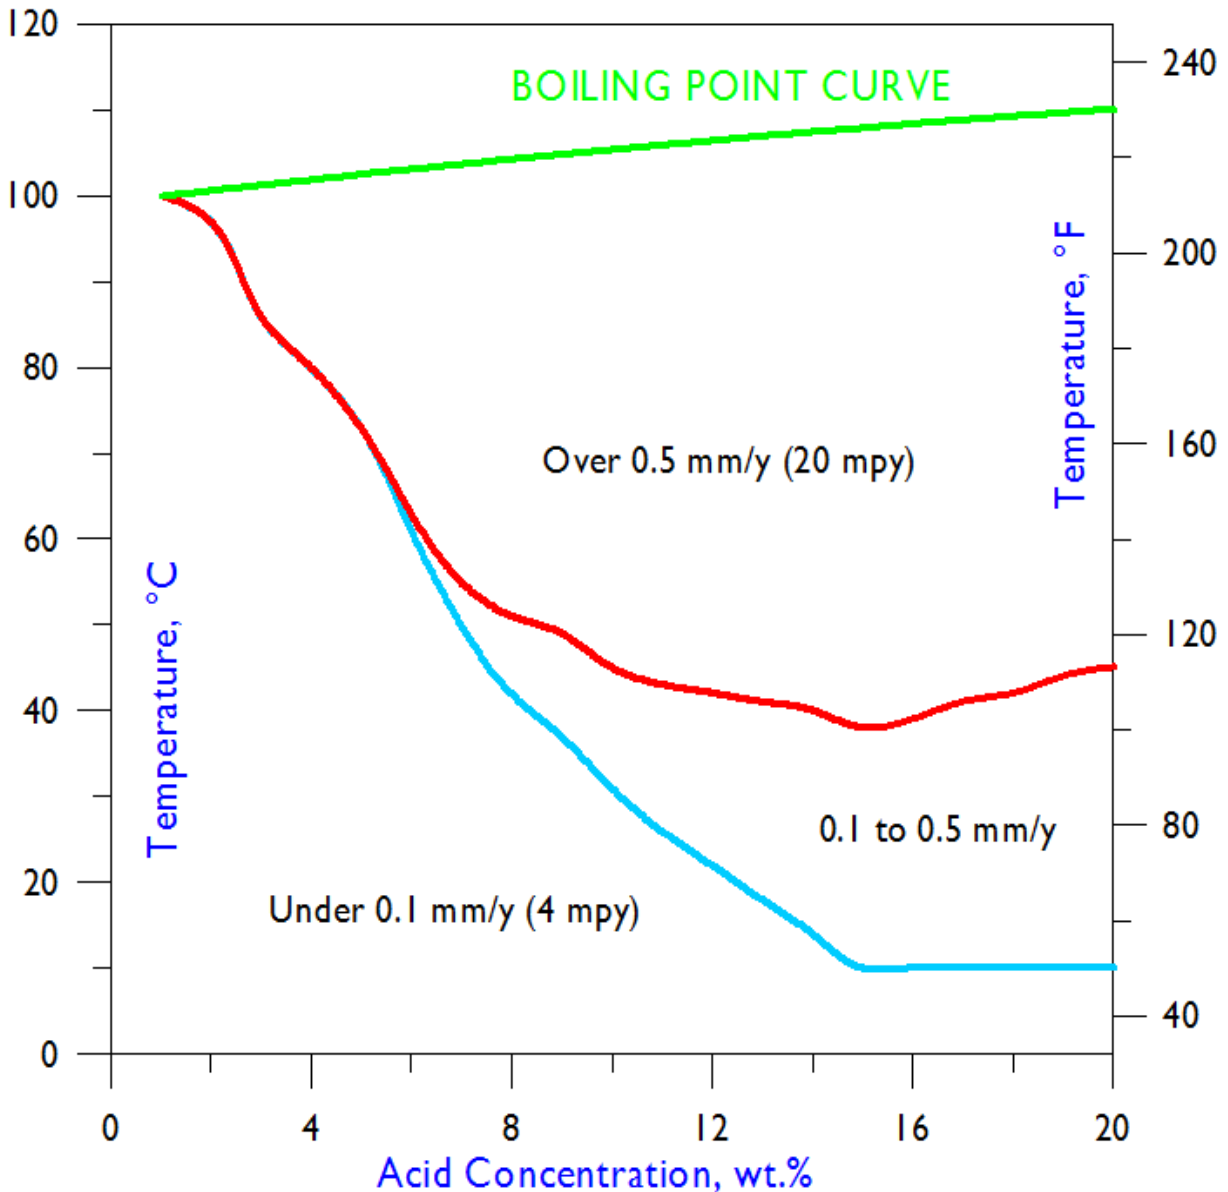

When using this data, please refer to our disclaimer located at www.haynesintl.com