

## HAYNES® 625 Alloy

### Hydrobromic Acid

Conc. Wt.%	50°F	75°F	100°F	125°F	150°F	175°F	200°F	225°F	Boiling
	10°C	24°C	38°C	52°C	66°C	79°C	93°C	107°C	
2.5	-	-	-	-	<0.01	-	<0.01	-	<0.01
5	-	-	-	-	<0.01	0.13	0.6	-	-
7.5	-	-	-	-	<0.01	<0.01	0.93	-	-
10	-	-	-	-	0.15	0.82	-	-	-
15	-	-	<0.01	0.3	0.64	-	-	-	-
20	-	0.01	0.16	0.33	0.65	-	-	-	-
25	-	-	-	-	-	-	-	-	-
30	-	-	0.11	0.21	0.34	0.72	-	-	-
40	-	-	0.08	0.15	0.25	0.42	0.79	-	-


All corrosion rates are in millimeters per year (mm/y); to convert to mils (thousandths of an inch) per year, divide by 0.0254.

Data are from Corrosion Laboratory Job 17-04.

All tests were performed in reagent grade acids under laboratory conditions; field tests are encouraged prior to industrial use.

# HAYNES® 625 Alloy

## Iso-Corrosion Diagram for Alloy 625 in Hydrobromic Acid

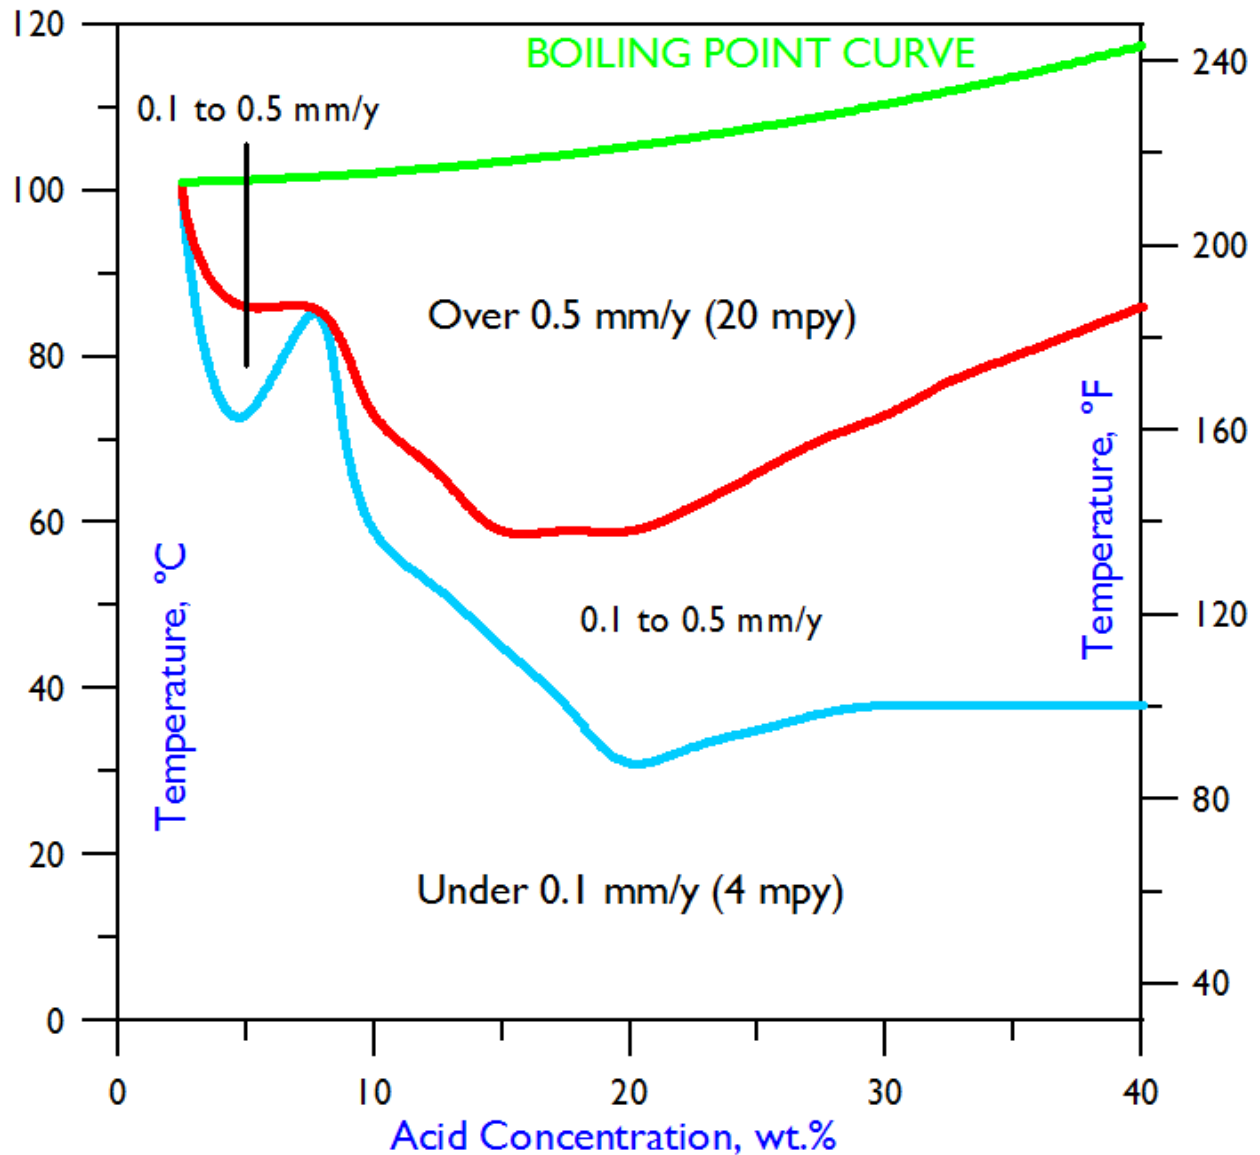

When using this data, please refer to our disclaimer located at [www.haynesintl.com](http://www.haynesintl.com)